

# CARBAZOLE DERIVATIVES AS HOLE TRANSPORTING MATERIALS FOR EFFICIENT SOLAR CELLS

Aistė Jegorovė<sup>1\*</sup>, Marytė Daškevičienė<sup>1</sup>, Vygintas Jankauskas<sup>2</sup>, Egidijus Karamauskas<sup>2</sup>, Vytautas Getautis<sup>1</sup>

<sup>1</sup>Department of Organic Chemistry, Kaunas University of Technology, Kaunas, Lithuania


<sup>2</sup>Institute of Chemical Physics, Vilnius University, Lithuania

\* aisilc@ktu.lt

## Introduction

Nowadays, people cannot imagine their life without electricity. Renewable energy sources, such as solar energy is an alternative for non-renewable energy generation. Solar cells are devices that convert absorbed light into electricity and silicon solar cells are currently the most commonly used technology to do that. However, it has its own drawbacks and other high efficiency solar cell technologies have been developed. The efficiency of hybrid Solar Cells, for example perovskite, has increased significantly over the last decade. However, there are obstacles that need to be addressed in order for it to see a widespread use. One of them is the use of expensive charge-transporting semiconductors such as Spiro-OMeTAD or fullerene derivatives to obtain efficient devices [1]. Therefore, there is a vigorous search for cheaper and simpler methods for the synthesis of organic semiconductors. Carbazole class compounds have attracted the attention of scientist due to their plain synthesis and simple purification methods [2]. The aim of this project is to synthesize inexpensive carbazole class materials, that would be suitable as hole-transporting semiconductors for perovskite solar cells.

## Synthesis

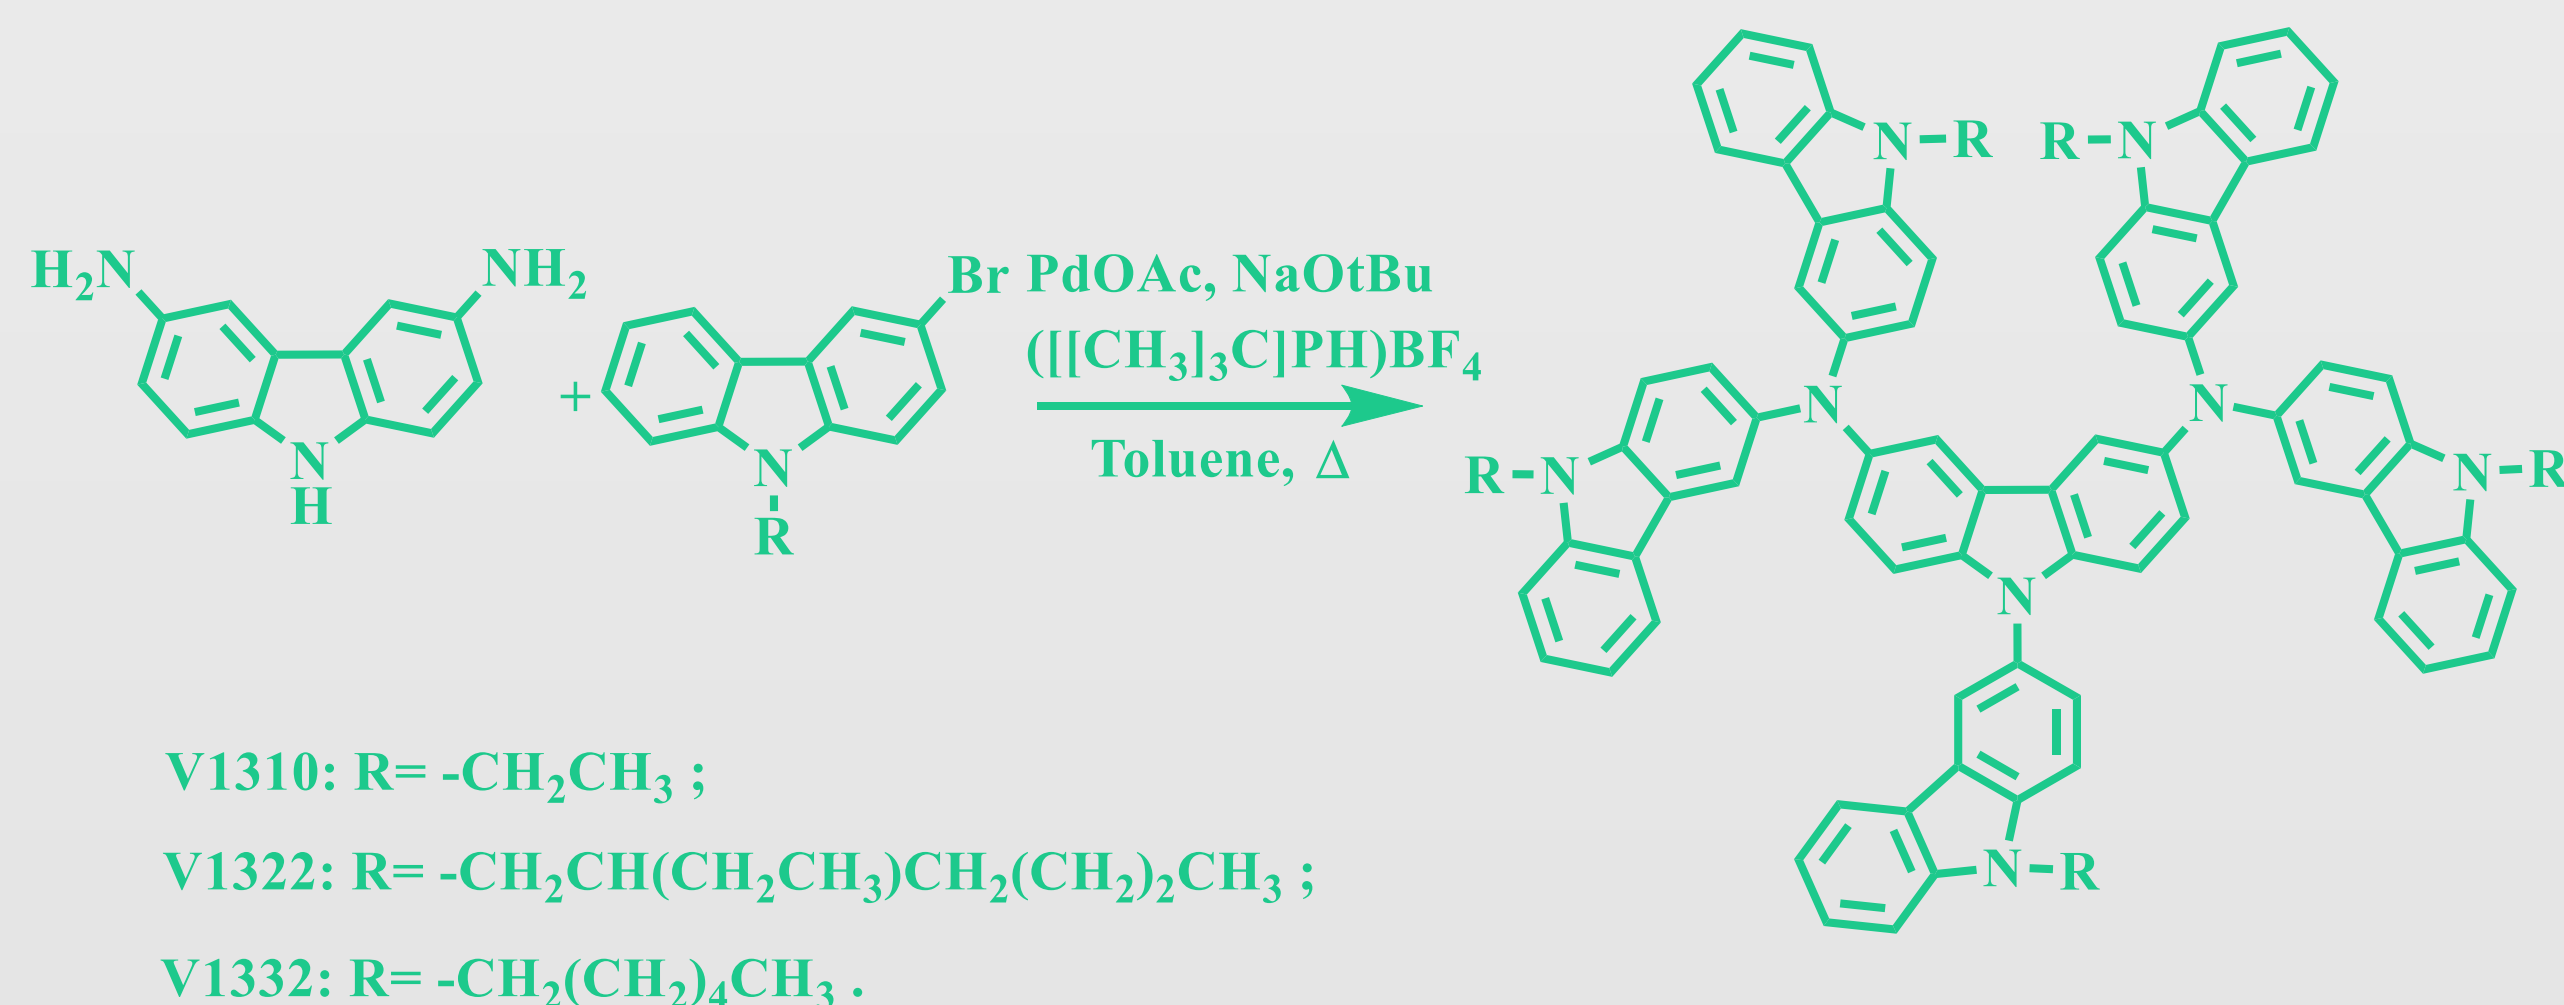

## Results

All target materials are amorphous and has thermal stability greater than 400 °C. The obtained data shows that ionization potential is near up to 5 eV. The charge carrier mobility is in range of  $3.7 \cdot 10^{-6} - 1.6 \cdot 10^{-6} \text{ cm}^2/\text{V}\cdot\text{s}$  in weak fields.

## Characteristics of new HTM's

Compound nr.	T <sub>g</sub> <sup>a</sup> , °C	T <sub>d</sub> <sup>b</sup> , °C	I <sub>p</sub> , eV	μ <sub>0</sub> , V · cm <sup>-1</sup> /s <sup>-1</sup>
V1310	216.8	511	4.86	1.6 · 10 <sup>-6</sup> <sup>c</sup>
V1323	97	411	4.99	3.7 · 10 <sup>-6</sup>
V1332	109.1	482	4.87	3.5 · 10 <sup>-6</sup>

<sup>a</sup> Glass transition temperature, extracted from the second DSC heating cycle;

<sup>b</sup> Decomposition temperature, corresponding to the 5% weight loss;

<sup>c</sup> V1310 + PC-Z (1:1).

## Conclusions

Based on the thermal and photoelectric properties, it can be stated that target materials can be used as HTM's in Solar cells.

## References

1. T. P. I. Saragi, T. Spehr et al. Spiro Compounds for Organic Optoelectronics, Chem. Rev. 107, 1011- 1065 (2007).
2. A. Singh et al. Bis(diphenylamine)-tethered carbazolyl anthracene derivatives as hole-transporting materials for stable and high-performance perovskite solar cells, ACS Appl. Energy Mater., 3, 11, 10752–10764 (2020)